arXiv:cond-mat/0301174v1 [cond-mat.supr-con] 13 Jan 2003

Superconducting Density of States from the Magnetic Penetration Depth of Electron-Doped Cuprates $La_{2-x}Ce_xCuO_{4-y}$ and $Pr_{2-x}Ce_xCuO_{4-y}$

John A. Skint, Mun-Seog Kim, and Thomas R. Lemberger
Department of Physics, Ohio State University, Columbus, OH 43210-1106

T. Greibe and M. Naito
NTT Basic Research Laboratories, 3-1 Morinosato Wakamiya, Atsugi-shi, Kanagawa 243, Japan

From measurements of the magnetic penetration depth, $\lambda(T)$, from 1.6 K to T_c in films of electron-doped cuprates $La_{2-x}Ce_xCuO_{4-y}$ and $Pr_{2-x}Ce_xCuO_{4-y}$ we obtain the normalized density of states, $N_s(E)$ at $T = 0$ by using a simple model. In this framework, the flat behavior of $\lambda^{-2}(T)$ at low T implies $N_s(E)$ is small, possibly gapped, at low energies. The upward curvature in $\lambda^{-2}(T)$ near T_c seen in overdoped films implies that superfluid comes from an anomalously small energy band within about $3k_BT_c$ of the Fermi surface.

I. INTRODUCTION

Pairing symmetry in the electron-doped cuprates $Ln_{2-x}Ce_xCuO_{4-y}$ (Ln = Nd, Pr, or La) is controversial. Phase-sensitive,[1] angle resolved photoemission spectroscopy,[2] and some penetration depth, $\lambda(T)$, measurements[3,4] on nominally optimally doped $Pr_{2-x}Ce_xCuO_{4-y}$ (PCCO) and $Nd_{2-x}Ce_xCuO_{4-y}$ (NCCO) samples suggest d-wave pairing. Other penetration depth measurements[5–8] and the absence of a zero-bias conductance peak in tunneling measurements[9,10] favor s-wave superconductivity. Recent penetration depth measurements on PCCO and $La_{2-x}Ce_xCuO_{4-y}$ (LCCO) films[7] and tunneling measurements on PCCO films[11] find evidence for a d- to s-wave pairing transition near optimal doping.

In this work we focus on understanding the unusual upward curvature that appears in $\lambda^{-2}(T)$ near T_c in overdoped films.[6,7] These are the films that show gapped behavior at low T, so they are especially important to understand. To that end, we develop a new analysis method which enables us to invert $\lambda^{-2}(T)$ to obtain the normalized superconducting density of states, $N_s(E)$, over a wide energy range. In this model, upward curvature means that superconducting effects are confined to energies less than about $3k_BT_c$. A fuller description, including data on many more films, will appear elsewhere.[12]

II. EXPERIMENTS

Films were prepared by molecular-beam epitaxy (MBE) on 10 mm × 10 mm × 0.35 mm (film La4) or 12.7 mm × 12.7 mm × 0.35 mm (films P1, P3, P7, La2, La5, and La7) $SrTiO_3$ substrates as detailed elsewhere.[13–17] The same growth procedures and parameters were used for all films of a given compound. Table I summarizes film properties. Films P1, P3, and P7 (La2, La5, and La7) are the underdoped, optimally doped, and overdoped PCCO (LCCO) films of Ref. 7. Ce concentrations, x, are measured by inductively coupled plasma spectroscopy to better than ±0.005. The films are highly c-axis oriented, and their ab-plane resistivities, $\rho_{ab}(T)$, are low.[7]

TABLE I. Properties of PCCO and LCCO films. Ce doping, x, is known to better than ±0.005. PCCO films are 1000Å thick, and LCCO films are 1250Å thick. T_c and ΔT_c are location and full-width of peak in σ_1. Absolute uncertainty in film thickness and $\lambda^{-2}(0)$ is ±10%. $\rho_{ab}(T_c^+)$ is the ab-plane resistivity just above T_c.

Film	Material	x	T_c [K]	ΔT_c [K]	$\lambda(0)$ [Å]	$\rho_{ab}(T_c^+)$ [$\mu\Omega$cm]
P1	PCCO	0.128	22.5	1.8	3100	40
P3	PCCO	0.145	24.2	1.0	1800	19
P7	PCCO	0.156	21.5	2.4	2000	18
La2	LCCO	0.087	28.7	0.8	3200	67
La4	LCCO	0.107	28.9	0.4	2300	37
La5	LCCO	0.112	29.3	0.9	2500	33
La7	LCCO	0.135	21.7	1.0	2300	15

We measure $\lambda^{-2}(T)$ with a low frequency two-coil mutual inductance technique described in detail elsewhere.[18,19] A film is centered between two small coils, and a current at 50 kHz in one coil induces eddy currents in the film. The second coil measures the attenuated magnetic field. We have checked that the *ac* field is too small to create vortices, except near T_c where $\lambda^{-2}(T)$ is much less than 1% of its value at $T = 0$. All of our conclusions are drawn from data taken in the linear response regime.

The film's sheet conductivity, $\sigma(T)d = \sigma_1(T)d - i\sigma_2(T)d$, with d = film thickness, is deduced from the measured mutual inductance. We define T_c and ΔT_c to be the temperature and full-width of the peak in σ_1. $\lambda^{-2}(T)$ is obtained from σ_2: $\lambda^{-2}(T) \equiv \mu_0\omega\sigma_2(T)$ (MKS units). Experimental noise is typically 0.2% of $\lambda^{-2}(0)$ at low T and is at least partly due to drift in amplifier gain. The $\pm 10\%$ absolute uncertainty in d is the largest source of error in $\lambda^{-2}(T)$. This uncertainty does not impact the temperature dependence of $\lambda^{-2}(T)/\lambda^{-2}(0)$. We estimate film-to-film uncertainty in $\lambda^{-2}(0)$ to be $\pm 5\%$. T_c's determined from resistivity and penetration depth measurements are identical.[6,7]

III. RESULTS

Figure 1 displays $\lambda^{-2}(T)$ for PCCO films.[7] Ref. 7 also shows data for LCCO. As detailed previously for films La2, La5, La7, P1, P3, and P7,[6,7,20] $\lambda^{-2}(T)$ at low T is quadratic in T at underdoping and exponentially flat at overdoping.

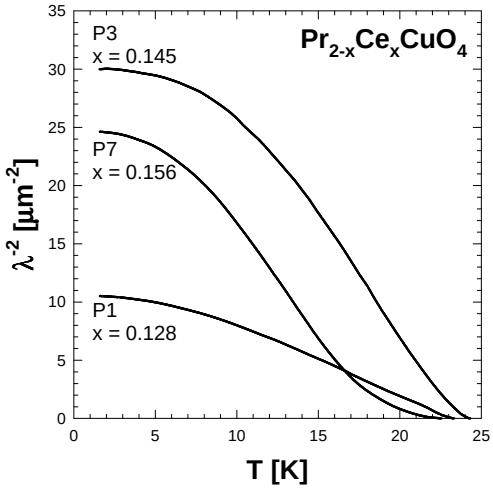

FIG. 1. $\lambda^{-2}(T)$ in three $Pr_{2-x}Ce_xCuO_4$ films. Film-to-film uncertainty in $\lambda^{-2}(0)$ is estimated to be $\pm 5\%$.

Upward curvature in $\lambda^{-2}(T)$ appears near T_c as seen for films P3 and P7. Interestingly, the temperature range over which upward curvature is observed does not increase monotonically with doping. A study of the doping dependence of $\lambda^{-2}(T)$ in a series of nine Pr_2CuO_4-buffered PCCO films reveals a similarly exaggerated foot at an intermediate overdoping level.[8,20] We emphasize that this upward curvature *is not* due to inhomogeneity.[21] Instead, we believe that it proceeds from an anomalously small order parameter, per the following.

IV. ANALYSIS

Our model extracts the essential elements of superconductivity. It starts with the clean-limit expression for the normalized superfluid fraction, $\rho_s(T)$:[22]

$$\rho_s(T) = 1 - 2\int_0^\infty dE \left(-\frac{\partial f(E)}{\partial E}\right) N_s(E,T), \tag{1}$$

where $N_s(E,T)$ is the normalized density of states, and $f(E) \equiv 1/(1+e^{E/k_BT})$ is the Fermi function. We justify the clean-limit assumption by estimating the scattering rate from measured resistivity just above T_c and $\lambda^{-2}(0)$, as discussed below. We invert $\lambda^{-2}(T)$ to get $N_s(E,0)$. N_s obtained this way is, in effect, the density of states for only those states that contribute substantially to ρ_s, not the full density of states. The situation is analogous to the density of states determined by tunneling, which is weighted by tunneling matrix elements. We assume $N_s(E,T)$ is a function of only $x \equiv E/\Delta_0(T)$, so its T dependence comes from the "order parameter", $\Delta_0(T)$. Theoretically, the dependence of the normalized order parameter, $\Delta_0(T/T_c)/\Delta_0(0)$, on T/T_c is quantitatively is insensitive to details of

the superconducting state. It is about the same for gapped s-wave and gapless d-wave superconductors, as captured by the following respective approximations:

$$\Delta_0(T/T_c)/\Delta_0(0) \approx \sqrt{\cos[\pi(0.04 + 0.96T/T_c)^2/2]}, \tag{2}$$

$$\Delta_0(T/T_c)/\Delta_0(0) \approx \sqrt{1-(T/T_c)^3}, \tag{3}$$

These two functions are very close, within 5%. We assume the same behavior for our films. Finally, we assume that $N_s(x)$ has a generic form: small at low energies, peaked at $E = \Delta_0(T)$, then unity. The abrupt drop from peak to unity accounts for upward curvature in ρ_s. This very simple form produces such good fits to our data that further refinement appears to be of limited usefulness. Specifically, we assume:

$$N_s(x) = \begin{cases} A(x-\delta)^n & \text{for } \delta \le x < 1-\epsilon \\ B & \text{for } 1-\epsilon \le x \le 1+\epsilon \\ 1 & \text{for } x > 1+\epsilon \end{cases} \tag{4}$$

The width of the peak in N_s is not a critical parameter. We typically choose it to be 20% of Δ_0, (*i.e.*, $\epsilon = 0.1$), in our fits. Our conclusions are insensitive to peak width if it is less than about 40%. δ is a number less than $1-\epsilon$ that allows N_s to have a minimum gap, $\Delta_{min} = \delta\Delta_0$. n and A determine N_s at energies below its peak, so they are used in fitting the first 5% drop in ρ_s. The peak energy, $\Delta_0(0)$, is the only free parameter for fitting the rest of $\rho_s(T)$. The height of the peak, B, is determined by conservation of states.

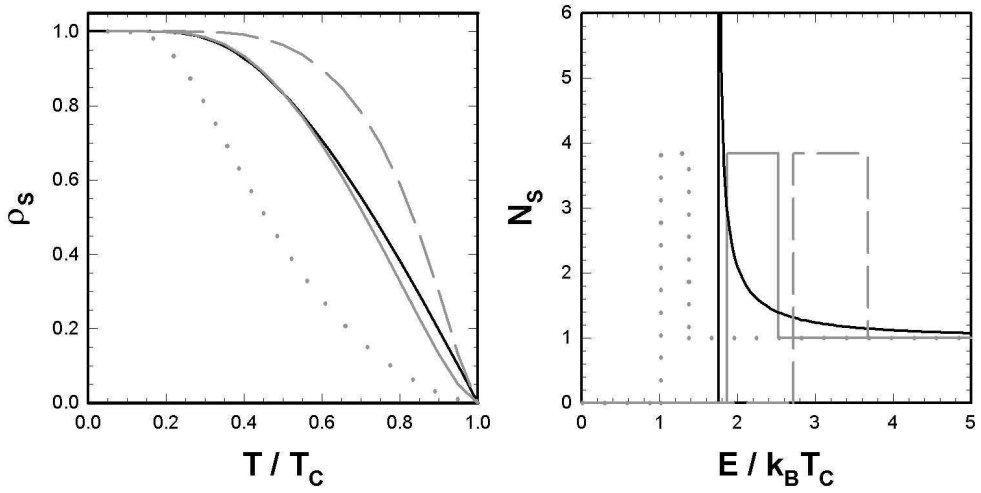

FIG. 2. Theoretical superfluid fraction, $\rho_s(T/T_c)$, and density of states, $N_s(E)$, (black lines, left and right panels) for weak-coupling s-wave superconductors. Gray lines are approximate densities of states (right panel) and resulting fits (left panel) calculated from the clean-limit model, Eq. (1). $\Delta_0(T/T_c)/\Delta_0(0)$ has the s-wave T-dependence of Eq. (2).

To get a feeling for the analysis, we apply it to obtain approximate densities of states from calculated superfluid fractions for weak-coupling s-wave and d-wave superconductors, shown as black curves in the left-hand panels of Figs. 2 and 3. The "fits" (gray curves) are calculated from the approximate densities of states in the right-hand panels. In both cases, a good fit is obtained when the low-energy edge of the peak in N_s is close to the peak in the exact density of states. To get a sense of how accurately we can locate the peak in N_s, we calculated $\rho_s(T)$ for three different peak positions, shown in Fig. 2. We emphasize that upward curvature in the ρ_s fits near T_c grows as the energy of upper edge of the peak in N_s decreases. Upward curvature is most obvious when superconductivity does not extend to energies above about $3k_BT_c$. In this case, states that contribute to superfluid density are accessible at lower temperatures than in the true density of states, which decreases slowly to unity at high energies, and the approximate $\rho_s(T)$ drops below the true $\rho_s(T)$ at high temperatures.

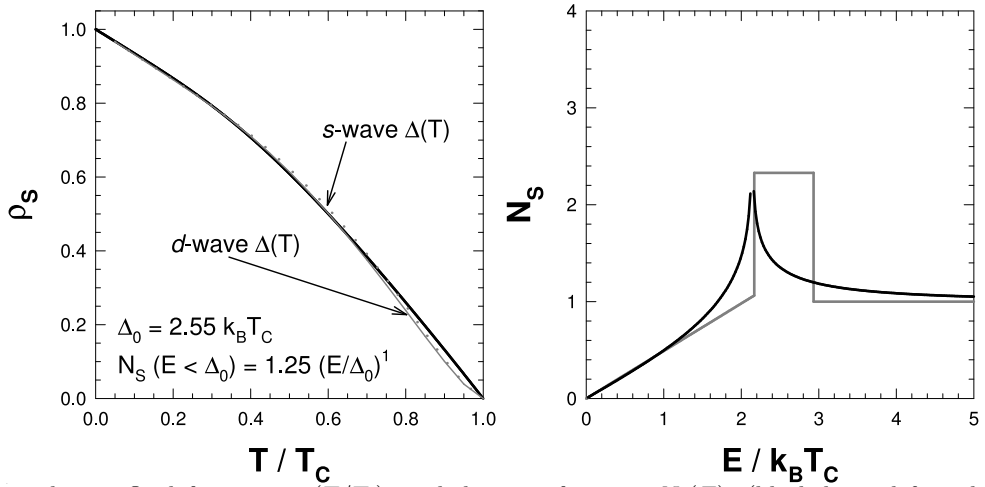

FIG. 3. Theoretical superfluid fraction, $\rho_s(T/T_c)$, and density of states, $N_s(E)$, (black lines, left and right panels) for weak-coupling d-wave superconductors. In the right panel, the gray line is an approximate density of states with its rectangular peak centered at $\Delta_0(0) = 2.55\ k_BT_c$. In the left panel, the thin gray and dotted gray lines are the resulting fits calculated using the approximate d-wave Eq. (3) and s-wave Eq. (2) gap T-dependences, respectively.

For the s-wave case, the s-wave gap approximation of Eq. (2) was used in the model calculations. $\Delta_{peak} \equiv (1-\epsilon)\Delta_0(0)$ is defined as the low-energy edge of the peak in N_s. For this s-wave "test case" $\Delta_{peak} = 1.87\ k_BT_c$, only 6% above the true weak-coupling gap value. For the d-wave case, both the approximate s-wave Eq. (2) and d-wave Eq. (3) gap T-dependences were used to calculate $\rho_s(T)$ from the same approximate $N_s(E)$. Figure 3 shows that there is little difference in quality between the two $\rho_s(T)$ fits, demonstrating the insensitivity of this analysis to the exact form of $\Delta_0(T/T_c)/\Delta_0(0)$.

We now turn to analysis of data. Results for one representative film are presented here, with more results found elsewhere[20,12]. All ρ_s curves in this section are calculated using the approximate d-wave gap T-dependence of Eq. (3), and with a peak width of 20% ($\epsilon = 0.1$). "Best fit" in this section refers to the approximate density of states that produces the most visually pleasing match to the experimental superfluid fraction. Resulting uncertainty in $\Delta_{peak} \equiv 0.9\Delta_0(0)$ is estimated to be $\pm 7.5\%$. Table II provides a summary of parameters from the analysis of several LCCO and PCCO films. For all fits in Table II N_s is gapless ($\delta = 0$).

Figure 4 shows data on film La4 (black curve) and two acceptable fits, obtained from gapless (solid gray fit) and gapped (dotted gray fit) densities of states. For the gapless case, $N_s \propto (E/\Delta_0(T))^3$ at low energy, and for the gapped case, N_s vanishes for $E \leq 0.7k_BT_c$. Relative to the gapless case, the peak in N_s shifts down in energy to compensate. At the level of accuracy of this analysis, we deem that $\rho_s(T)$ fits produced by these two different densities of states are both acceptable. N_s may have a small gap, perhaps as big as k_BT_c. This is true for all films, even those that show quadratic behavior at low T.[12]

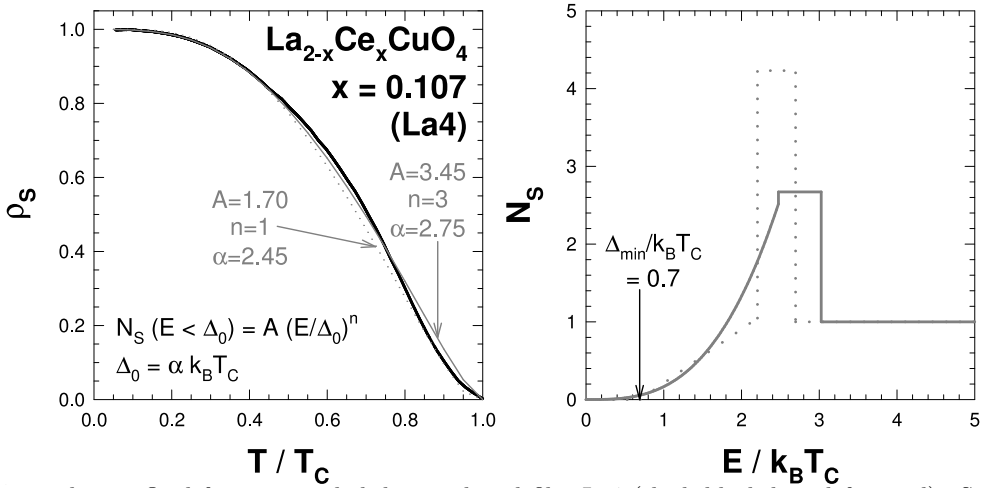

FIG. 4. Experimental superfluid fraction in slightly overdoped film La4 (thick black line, left panel). Solid gray lines are $\rho_s(T)$ (left panel) and N_s (right panel) for the case of no gap. Dotted gray lines are $\rho_s(T)$ and N_s for the case of a minimum gap, $\Delta_{min} = 0.7\ k_BT_c$.

Fits of similar or better quality can be obtained for all of the films that we have studied.[8,12] This is remarkable considering the simplicity of the model. We conclude that upward curvature in $\lambda^{-2}(T)$ near T_c indicates that superfluid comes from states with energies less than about $3k_BT_c$. Either superconductivity does not extend to higher energies, or higher energy states do not contribute significantly to superfluid density because their group velocity is small, or there is a strong k-dependent scattering rate that diminishes their current carrying ability.

TABLE II. Parameters from density-of-states analysis of experimental superfluid density in $Pr_{2-x}Ce_xCuO_4$ and $La_{2-x}Ce_xCuO_4$ films. A and n characterize N_s below its peak: $N_s[E/\Delta_0(T)] = A[E/\Delta_0(T)]^n$ for $0 < E/\Delta_0(T) < 0.9$. $\Delta_{peak} = 0.9\Delta_0(0)$ is the low-energy edge of the peak in N_s. Uncertainty in the best-fit value of Δ_{peak} is $\approx \pm 7.5\%$.

Film	x (± 0.005)	A	n	Δ_0/k_BT_c	Δ_{peak}/k_BT_c
P1	0.128	2.30	2	2.45	2.20
P3	0.145	2.00	3	2.30	2.07
P7	0.156	2.80	3	1.95	1.76
La2	0.087	1.50	2	3.05	2.74
La4	0.107	3.45	3	2.75	2.48
La5	0.112	2.80	3	2.35	2.12
La7	0.135	2.50	3	1.25	1.12

We now return to our starting assumption that the films are clean, in the sense that the electron mean free path is much larger than the superconducting coherence length, or, in other words, that the scattering rate, τ_{scatt}^{-1}, is much smaller than the order parameter, Δ_{peak}. For present purposes, the usual weak-coupling s-wave relationship among superfluid density, $n_s(0)$, total carrier density, n, and τ_{scatt}^{-1} captures the decrease in $n_s(0)$ with scattering: $n_s(0)/n \approx (1 + \hbar\tau_{scatt}^{-1}/\pi\Delta_{peak})^{-1}$, so samples are "clean" if $\gamma \equiv \hbar\tau_{scatt}^{-1}/\pi\Delta_{peak}$ is small.[22] τ_{scatt}^{-1} can be estimated from the resistivity just above T_c and $\lambda(0)$:

$$\tau_{scatt}^{-1} \approx \frac{\rho_{ab}(T_c^+)}{\mu_0\lambda^2(0)}. \tag{5}$$

This approximation follows from the simple expressions for penetration depth and resistivity: $\lambda^{-2}(0) = n_s(0)e^2\mu_0/m \approx ne^2\mu_0/m$, and $\rho_{ab} \approx m/n_se^2\tau_{scatt}$. Using Δ_{peak} from Table II and τ_{scatt}^{-1} calculated from experimental resistivities and penetration depths (Table I), we find that γ is indeed small, varying between 0.17 and 0.23 for PCCO and 0.14 and 0.23 for LCCO.[20,12]

It is interesting to explore the quantitative implications of a small γ in the contexts of s-wave and d-wave superconductivity. In the context of s-wave theory, the deduced γ's imply that perfectly clean films would have superfluid densities about 20% larger than those reported here, a small correction. In the context of dirty d-wave theory,[23] on the other hand, the deduced γ's imply that cleaner films would have superfluid densities perhaps twice those reported here, if scattering is in the unitary limit. That would mean that $\lambda^{-2}(0)$ of optimally-doped PCCO and LCCO films would be about double that of the closely-related hole-doped compound, LSCO.[24] This seems unreasonable to us, so we feel that if superconductivity is d-wave, scattering must be weak, rather than unitary. But if so, then it is difficult to understand why we do not observe the crossover from T to T^2 at low T predicted by dirty d-wave theory.

V. CONCLUSION

Our phenomenological analysis finds that upward curvature that develops in $\lambda^{-2}(T)$ upon overdoping with Ce indicates that the energy scale for superconductivity decreases anomalously. For underdoped films, on the other hand, the peak in the superconducting density of states appears at a reasonable energy, about 2.5 k_BT_c. The reason for the decrease needs to be found.

The effective superconducting density of states, $N_s(E)$, is low at low energies for every doping level and could vanish for E less than some minimum gap, Δ_{min}. This behavior conflicts with the behavior expected for clean d-wave superconductors. Scattering rates deduced from $\rho_{ab}(T_c^+)\lambda^{-2}(0)$ can account for the absence of a crossover from quadratic to T-linear behavior, as predicted by dirty d-wave theory, but only if one accepts that the superfluid density of very clean LCCO and PCCO are about twice that of their hole-doped cousin, LSCO. We note that measurements on PCCO films deposited onto a buffer layer instead of directly onto $SrTiO_3$ display exponentially flat behavior at low T regardless of Ce concentration, consistent with a gapped density of states.[8]

ACKNOWLEDGMENTS

This work was supported in part by grant nsf-dmr 0203739.

---

[1] C. C. Tsuei and J. R. Kirtley, Phys. Rev. Lett. **85**, 182 (2000).
[2] N. P. Armitage, D. H. Lu, D. L. Feng, C. Kim, A. Damascelli, K. M. Shen, F. Ronning, Z.-X. Shen, Y. Onose, Y. Taguchi, and Y. Tokura, Phys. Rev. Lett. **86**, 1126 (2001).
[3] J. D. Kokales, P. Fournier, L. V. Mercaldo, V. V. Talanov, R. L. Greene, and S. M. Anlage, Phys. Rev. Lett. **85**, 3696 (2000).
[4] R. Prozorov, R. W. Giannetta, P. Fournier, and R. L. Greene, Phys. Rev. Lett. **85**, 3700 (2000).
[5] L. Alff, A. Beck, R. Gross, A. Marx, S. Kleefisch, Th. Bauch, H. Sato, M. Naito, and G. Koren, Phys. Rev. B **58**, 11197 (1998).
[6] John A. Skinta, Thomas R. Lemberger, T. Greibe, and M. Naito, Phys. Rev. Lett. **88**, 207003 (2002).
[7] John A. Skinta, Mun-Seog Kim, Thomas R. Lemberger, T. Greibe, and M. Naito, Phys. Rev. Lett. **88**, 207005 (2002).
[8] Mun-Seog Kim, John A. Skinta, Thomas R. Lemberger, T. Greibe, and M. Naito (unpublished).
[9] S. Kashiwaya, T. Ito, K. Oka, S. Ueno, H. Takashima, M. Koyanagi, Y. Tanaka, and K. Kajimura, Phys. Rev. B **57**, 8680 (1998).
[10] L. Alff, S. Meyer, S. Kleefisch, U. Schoop, A. Marx, H. Sato, M. Naito, and R. Gross1, Phys. Rev. Lett. **83**, 2644 (1999).
[11] Amlan Biswas, P. Fournier, M. M. Qazilbash, V. N. Smolyaninova, Hamza Balci, and R. L. Greene, Phys. Rev. Lett. **88**, 207004 (2002).
[12] John A. Skinta, Mun-Seog Kim, Thomas R. Lemberger, T. Greibe, and M. Naito (unpublished).
[13] M. Naito, H. Sato, and H. Yamamoto, Physica C **293**, 36 (1997).
[14] M. Naito and H. Sato, Appl. Phys. Lett. **67**, 2557 (1995).
[15] H. Yamamoto, M. Naito, and H. Sato, Phys. Rev. B **56**, 2852 (1997).
[16] M. Naito and M. Hepp, Jpn. J. Appl. Phys. Lett. **39**, 485 (2000).
[17] M. Naito and M. Hepp, Physica C **357-360**, 333 (2001).
[18] S. J. Turneaure, E. R. Ulm, and T. R. Lemberger, J. Appl. Phys. **79**, 4221 (1996).
[19] S. J. Turneaure, A. A. Pesetski, and T. R. Lemberger, J. Appl. Phys. **83**, 4334 (1998).
[20] J. A. Skinta, Ph.D. thesis, Ohio State University, 2002.
[21] We have observed upward curvature in λ^{-2} near T_c in many films, but never at temperatures below the fluctuation peak in σ_1. We ascribe upward curvature with non-zero σ_1 to film inhomogeneity.
[22] M. Tinkham, *Introduction to Superconductivity*, 2nd ed. (McGraw-Hill, New York, 1996).
[23] P. J. Hirschfeld and N. Goldenfeld, Phys. Rev. B **48**, 4219 (1993).
[24] C. Panagopoulos, B. D. Rainford, J. R. Cooper, W. Lo, J. L. Tallon, J. W. Loram, J. Betouras, Y. S. Wang, and C. W. Chu, Phys. Rev. B **60**, 14617 (1999).